



Enhancing S.I. Engine Performance with Metal-Doped Zeolite X Derived from Rice Husk

Aasthiya Bharathinathan¹†, Karthikeyan Duraisamy¹ and Sethuraman Narayanan²

¹Department of Mechanical Engineering, Annamalai University, Chidambaram, Tamil Nadu, India

²Department of Mechanical Engineering, IFET College of Engineering, Villupuram, Tamil Nadu, India

†Corresponding author: Aasthiya B; aasthiyabharathi96@gmail.com

Abbreviation: Nat. Env. & Poll. Technol.

Website: www.neptjournal.com

Received: 28-05-2025

Revised: 09-07-2025

Accepted: 16-07-2025

Key Words:

Synthesis of rice husk
X-zeolite
NOx emission
Catalytic converter

Citation for the Paper:

Bharathinathan, A., Duraisamy, K., and Narayanan, S., 2026. Enhancing S.I. engine performance with metal-doped zeolite X derived from rice husk. *Nature Environment and Pollution Technology*, 25(1), B4356. <https://doi.org/10.46488/NEPT.2026.v25i01.B4356>

Note: From 2025, the journal has adopted the use of Article IDs in citations instead of traditional consecutive page numbers. Each article is now given individual page ranges starting from page 1.



Copyright: © 2026 by the authors

Licensee: Technoscience Publications

This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

ABSTRACT

The increasing prevalence of harmful NOx emissions from gasoline engines necessitates the development of alternatives to traditional three-way catalytic converters. This study investigates the potential of low-cost zeolites derived from rice husk ash as a promising alternative. Na-X zeolites derived from rice husk ash were characterized using X-ray fluorescence (XRF), Fourier-transform infrared spectroscopy (FTIR), X-ray diffraction (XRD), and field emission scanning electron microscopy (FESEM) to determine their structural properties and morphology. These zeolites were then modified with copper (Cu) and iron (Fe) ions to create Cu-X and Fe-X zeolite catalysts. The catalysts were wash-coated onto cordierite honeycomb monoliths and integrated and properly housed in a steel casing catalytic converter and fitted near the exhaust manifold of a twin-cylinder nano-engine. Engine performance and emissions were evaluated under various operating loads (4, 7, 10, 13, and 16 kW). NOx, CO, HC, CO₂, and O₂ emissions were measured using an AVL DI gas analyzer. The results demonstrated that the developed Cu-X and Fe-X zeolite converters significantly outperformed the conventional catalytic converter in reducing NOx emissions, while maintaining comparable performance for other pollutants. The enhanced NOx reduction capabilities of the zeolite catalysts can be attributed to their unique structural properties and the synergistic effect of the copper and iron ions.

INTRODUCTION

Zeolites, synthetic crystalline aluminosilicates, have become indispensable across various industries due to their unique structural properties and remarkable performance. Zeolite X, in particular, features a three-dimensional framework of interconnected tetrahedral units composed primarily of silicon (Si) and aluminum (Al) atoms. These tetrahedra are linked by oxygen atoms (O), forming a network of channels and cavities that define the material's high surface area and ion-exchange capabilities.

The discovery of zeolites dates back to 1756 when Cronstedt identified stilbite, the first known zeolite, after observing its rapid water loss upon heating, resembling boiling. The term "zeolite" originates from the Greek words *zeo* (to boil) and *lithos* (stone) (Edanol et al. 2018). Zeolites typically follow the empirical formula $M_n/Al_2O_3 \cdot xSiO_2 \cdot yH_2O$, where M represents an exchangeable cation with valence n. Commonly, M includes Group I or II ions, though other metal, non-metal, and organic cations may also be used to balance the negative charge introduced by aluminum in the structure (Saceda et al. 2011).

Rice husk, an abundant agricultural byproduct, consists mainly of the husk along with rice straw, plant matter, and other organic components. Significantly, rice husk contains over 90% silica, making it a cost-effective and plentiful source of high-quality amorphous silica. Extensive research has been devoted to extracting silica from rice husk for various applications, including the production of nano-

silica (Ma et al. 2014). Silica's versatility enables its use in a wide range of industries, such as ceramics, chromatography, adhesives, detergents, electronics, pharmaceuticals, and vegetable oil processing. Rice husk ash (RHA), produced by burning rice husk, has gained attention as a low-cost raw material for synthesizing silica powders and gels (Das et al. 2022). However, silica extracted from RHA may contain impurities like CaO, Al₂O₃, and MgO in addition to SiO₂. These impurities must be considered and, if necessary, removed depending on the intended application (Hassan & Jaaron 2021).

Several studies have focused on synthesizing zeolites from RHA-derived silica. Dalai et al. (2010) synthesized zeolites such as NaX, PC, analcime, and hydroxysodalite using standard procedures and reported evidence of new phase formation at elevated temperatures through XRD analysis. Yusof et al. (2010) successfully synthesized high-purity Zeolite NaY at a controlled temperature of 600°C, utilizing seeding and aging processes to eliminate undesired phases. Saceda et al. (2011) compared silica extraction from both rice husk (RH) and RHA, concluding that RH is a more efficient source for Zeolite NaY synthesis due to simpler extraction and higher recovery. Silica from RH consisted solely of SiO₂, while that from RHA contained 97.56% SiO₂ along with 2.14% K₂O and 0.31% Al₂O₃. The resulting Zeolite NaY exhibited a high BET surface area of 882 m².g⁻¹ and a micropore volume of 0.38 cm³.g⁻¹, typical of Y-type zeolite structures. Setthaya et al. (2013) synthesized faujasite and analcime zeolites using RHA and metakaolin through a dissolution-precipitation method followed by hydrothermal treatment. They found that faujasite formed at lower hydrothermal temperatures, whereas analcime developed under higher temperatures and prolonged synthesis durations. They concluded that time and temperature affect phase transitions and crystal development, while stirring duration impacts specific surface area but not zeolite type. Santasnachok et al. (2014) synthesized pure Na-A and Na-X zeolites using alkali fusion followed by extraction, residue removal, and hydrothermal treatment. Zeolite A was synthesized at 90°C for 10 to 24 h using Si/Al molar ratios of 0.5 to 1.0. NaX zeolite was produced under the same conditions with Si/Al ratios ranging from 1.5 to 2.0. Both zeolites were tested for cadmium ion removal, with Na-A proving more effective, reducing Cd²⁺ concentrations below the WHO limit of 0.01 mg.L⁻¹. Pandiangan et al. (2017) reported successful synthesis of zeolite X from rice husk silica and aluminum, confirmed by Fourier-transform infrared (FTIR), X-ray diffraction (XRD), and Field emission Scanning Electron Microscopy (FESEM) analysis. Furthermore, transesterification experiments verified by

GC-MS demonstrated the catalytic activity of zeolite X in converting palm oil into biodiesel.

Substantial research has explored the influence of varying hydrothermal conditions on zeolite synthesis (Saleh et al. 2018). The literature consistently supports alkali fusion combined with hydrothermal treatment as an efficient strategy for producing various zeolite types, such as X, Y, NaX, NaY, NaP, PC, analcime, and hydroxysodalite—from rice husk ash with different compositions. The central problem addressed in this study is the substantial emission of nitrogen oxides (NO_x) from gasoline engines, which significantly contributes to air pollution and poses serious environmental and health risks. Traditional catalytic converters often show limited effectiveness under the oxygen-rich conditions typical of gasoline engine exhaust. Hence, there is a pressing need for more efficient and sustainable catalysts. The primary objective of this research is to develop novel zeolite-based catalysts synthesized from rice husk ash, an eco-friendly and low-cost silica source. These zeolites are further modified with copper and iron ions to improve their catalytic performance for NO_x reduction. The study aims to assess the effectiveness of Cu-X and Fe-X catalysts under different engine operating conditions and compare their performance with conventional catalytic converters. Ultimately, this research aspires to contribute to cleaner emission control technologies for gasoline engines, supporting the advancement of more environmentally friendly transportation systems.

MATERIALS AND METHODS

The best raw material of rice husk (RH) used for the production of zeolites-x. Initially, the formation of zeolites-X from silica, therefore silica is produced by the acid treatment of RH during incineration. Here, the main precursor for the synthesis of the silica source is dissolved rice husk. Raw rice husks undergo a multi-step purification process to yield a refined ash product. Initially, the husks are sieved to remove impurities like clay and dust. Following this, they are steeped in a 10M concentrated hydrochloric acid solution. The treated husks are then thoroughly washed, filtered, and air-dried. The final step involves calcination at 850°C for 5 hrs. Initially, 50 g of silica and 20 of sodium hydroxide were dissolved in 500 mL of distilled water. Then the mixture was agitated with a magnetic stirrer. After a little while, the required amount of 10 g of sodium hydroxide and 10 g of aluminum oxide were both dissolved in separate beaker, in addition, the solution formed into sodium aluminate, and the pH value is 11, occur seems to have a bluish color. The mixture of sodium aluminate dissolved in silicate solution. Stir well until 4hrs around 250 rpm until the silica dissolves clearly.

Table 1: The Elemental Composition of Zeolite X.

METAL OXIDES	RRH %	IN-HOUSE MADE ZEOLITE X%
SiO ₂	59.57	67.612
Al ₂ O ₃	3.58	15.675
Na ₂ O	0.58	8.789
P ₂ O ₅	18.85	1.789
K ₂ O	6.85	0.9
CaO	1.95	0.971
TiO ₂	0.24	0.303
Fe ₂ O ₃	0.14	4.476
MgO	4.58	0.00
Cl	0.58	0.00
SO ₃	3.08	0.00
MoO ₃	0.02	0.00

At last, the sample is obtained. Take it out and wash it several times until the impurities are removed. The obtained place in the oven at 100°C for 24 h. At last, the obtained zeolite X-like material.

XRF

The elemental composition of the raw rice husk (RRH) and the synthesized zeolite X was determined using X-ray fluorescence (XRF) spectroscopy. Table 1 revealed a significant increase in the silica (SiO₂) content from 59.57 wt.% in RRH to 67.612 wt.% in the final zeolite X product, indicating the successful enrichment of silica during the synthesis process. Silica (SiO₂) forms the primary framework of zeolite X, consisting of tetrahedrally coordinated silicon atoms linked by oxygen atoms to create a three-dimensional network. Alongside SiO₂, sodium oxide (Na₂O) and aluminium oxide (Al₂O₃) constitute the fundamental components of the zeolitic structure. Notably,

Na₂O was present at 8.789 wt.% in the synthesized material, balancing the negative charge introduced by Al atoms within the framework. These sodium ions are located within the pores of the zeolite and are exchangeable with other cations such as K⁺, Ca²⁺, and Mg²⁺, providing versatility for ion exchange and catalytic applications. The presence of Al₂O₃ further enhances the structural stability and acidic properties of the material, which are crucial for catalytic performance. Additionally, trace quantities of K₂O, CaO, TiO₂, and Fe₂O₃ were detected in the final product. These minor oxides may contribute to the modulation of the zeolite's physicochemical and catalytic behavior

FTIR

FTIR spectroscopy was employed to analyze the functional groups and structural features of the synthesized zeolite X. Fig.1 revealed characteristic absorption bands that are consistent with the framework vibrations of zeolitic materials. A strong and broad peak near 1000 cm⁻¹ corresponds to the asymmetric stretching vibrations of Si–O–Si, confirming the formation of the zeolite's tetrahedral silica framework. A distinct signal observed at 880 cm⁻¹ is attributed to internal ring vibrations, which are typically associated with specific pore structures and crystalline arrangements within zeolite frameworks. A broad band around 3000 cm⁻¹ indicates the presence of hydroxyl (–OH) groups, likely arising from adsorbed silanol species or water molecules on the surface. The presence of water is further supported by a peak near 1800 cm⁻¹, which is attributed to bending vibrations of molecularly adsorbed H₂O. An additional feature at approximately 2350 cm⁻¹ is ascribed to adsorbed atmospheric CO₂, commonly seen in FTIR spectra of porous materials exposed to ambient air. Moreover, C–H stretching bands overlapping around 3000 cm⁻¹ suggest the presence of residual organic species from synthesis or precursor materials. The high transmittance

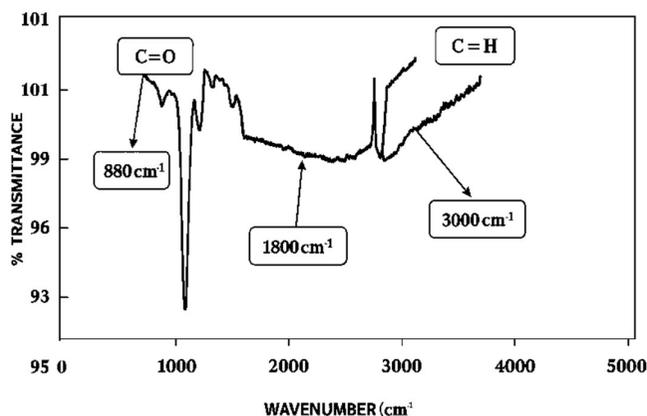


Fig. 1: FTIR Diffraction of in-house-made Zeolite X.

observed in the 4000–5000 cm^{-1} region indicates the absence of significant absorption bands in this range, confirming the structural purity of the sample. Overall, the FTIR data validate the successful synthesis of zeolite X and reflect its compositional and structural fidelity.

FESEM

FESEM was employed to investigate the surface morphology and microstructure of the synthesized zeolite X. As shown in Fig. 2, the sample consists of relatively small particles with an average size in the $\sim 1 \mu\text{m}$ range, which aligns well with typical zeolite particle size distributions. The particles exhibit an irregular and porous morphology, featuring a honey comb like framework with interconnected pores, characteristic of zeolite X. This microstructure is beneficial for catalytic applications due to enhanced surface area and accessibility to active sites. Slight aggregation of particles was observed, Fig. 3 shows potentially caused by electrostatic interaction during the synthesis and drying processes. Moreover, the particle surfaces appear rough and textured, suggesting the presence of surface defects or structural irregularities, which can significantly influence the material's adsorption and catalytic performance. These morphological features collectively confirm the successful formation of zeolite X with a structure suitable for advanced catalytic applications.

Preparation of Cu-X and Fe-X Zeolite Catalysts

Cu-X and Fe-X zeolite catalysts were synthesized via ion-exchange of zeolite X, followed by washcoating onto cordierite monoliths using a silica-based slurry to achieve 15 wt.% coating and thermal activation.

To prepare the metal-exchanged zeolite catalysts, 10 g of zeolite X powder synthesized from rice husk ash was subjected to an ion-exchange process. The powder was dispersed in 1000 mL of 0.05 M cupric chloride dihydrate

($\text{CuCl}_2 \cdot 2\text{H}_2\text{O}$, Fisher Scientific) solution and stirred vigorously using a magnetic stirrer at ambient temperature for 24 h. The suspension was vacuum-filtered and rinsed thoroughly with deionized water to remove excess ions. For the Fe-exchanged zeolite, ferrous chloride tetrahydrate ($\text{FeCl}_2 \cdot 4\text{H}_2\text{O}$, Fisher Scientific) was used instead of cupric chloride. The resulting solids were dried in an oven and calcined at 550°C for 6 h to activate the catalysts.


Cordierite monoliths (supplied by Bocent Advanced Ceramics Co., Ltd.) were used as substrates. These monoliths had a cell density of 400 CPSI, a wall thickness of 0.17 mm, and were 90 mm in both diameter and length. One monolith was platinum-coated, and the other was uncoated, serving as a control.

The washcoating slurry consisted of 20 wt. % Cu-X zeolite, 4 wt. % silica gel, and distilled water as the solvent. Each monolith was dipped in the slurry for one minute, and excess slurry was blown out with compressed air through both ends. The monoliths were dried in a muffle furnace at 120°C for 2 h, and the process was repeated until the washcoat loading reached 15 wt.% of the monolith's weight. Finally, the coated monoliths were calcined at 500°C for 5 h. The same washcoating and thermal treatment protocol was applied to prepare Pt-Fe-zeolite and Fe-X zeolite-coated monoliths.

Fabrication of Catalytic Converter-Catalytic Activity Tests on a Twin-Cylinder Petrol Engine Were Conducted Using Two Fabricated Catalytic Converter Types

Type 1

Two catalytic converters were fabricated with dimensions matching the original equipment manufacturer's catalytic converter. A Pt-Cu-X zeolite-coated monolith was tightly wrapped with resilient matting (to dampen vibrations) and then mounted in a steel casing. Inlet and outlet cones were

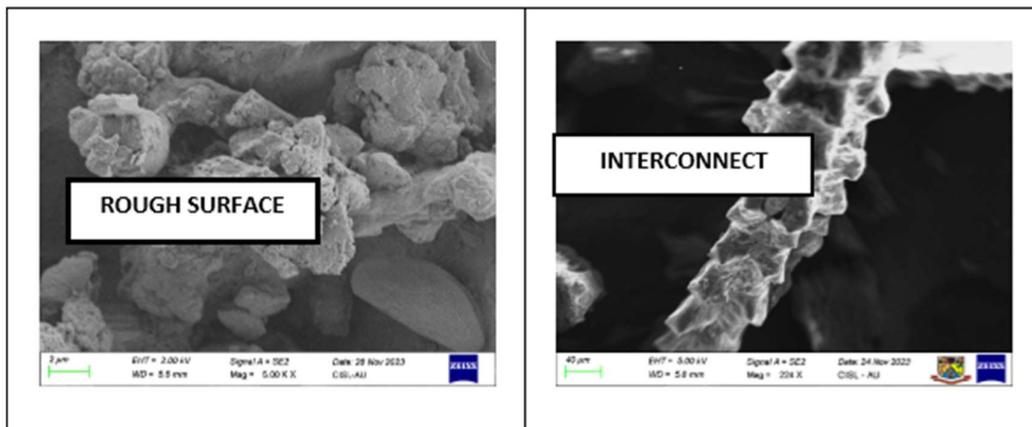

Figs. 2 and 3: Morphology of Raw rice husk and the morphology of in-house-made zeolite X.

welded to both ends of the casing. The catalytic converter was firmly attached to the engine's exhaust pipe. A stainless steel cover acted as a heat shield. Pt-Fe- coated monolith catalytic converters were fabricated using the same procedure. Fig 4 shows the in-house and commercial catalytic converters, respectively.

Type 2:

For the different configuration, a commercially sourced platinum (Pt)- coated monolith and a conventionally prepared copper-exchanged zeolite X (Cu-X) coated monolith were meticulously assembled within a welded steel casing, equipped with integrated inlet and outlet cones. This design strategically combined the catalytic activity of the Pt- coated monolith with the NO_x reduction capabilities of the (Cu-X) zeolite coating. To ensure secure installation within the engine's exhaust system, appropriate mounting provisions were incorporated. A similar fabrication process was employed to create a catalytic converter utilizing a Pt-coated monolith and an iron-exchanged zeolite X (Fe-X) coated monolith. Fig. 5 depicts the deNO_x catalytic converter, which was manufactured in-house. The second configuration

involved the assembly of a commercially obtained platinum coated monolith and a custom-prepared copper-exchanged zeolite X (Cu-X) coated monolith within a steel casing. This casing was then proficiently welded and fitted with inlet and outlet cones to facilitate gas flow. The resulting catalytic converter was securely integrated into the engine's exhaust pipe. A parallel fabrication process was used to create a separate catalytic converter, this time combining a platinum-coated monolith with an iron-exchanged zeolite X (Fe-X) coated monolith. It shows a visual representation of the deNO_x catalytic converter, which was produced within our own facilities.

Experimental Setup

The test engine for this research was a 624 cc, four-stroke, twin-cylinder, water-cooled spark-ignition type (Table 2). Fig. 6 describes the test facility, which comprised the engine fixed on a test bed and directly linked to an eddy current dynamometer. This dynamometer provided precise engine loading control and switching capabilities. The experiment used an AVL-Di gas analyzer utilized for the accurate measurement of CO, HC, NO_x, and O₂ emissions. Exhaust

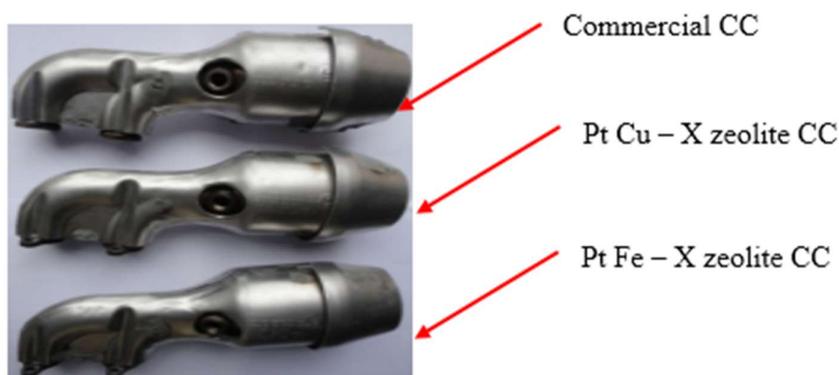


Fig. 4: Photographic view of an in-house-made and commercial catalytic converter.

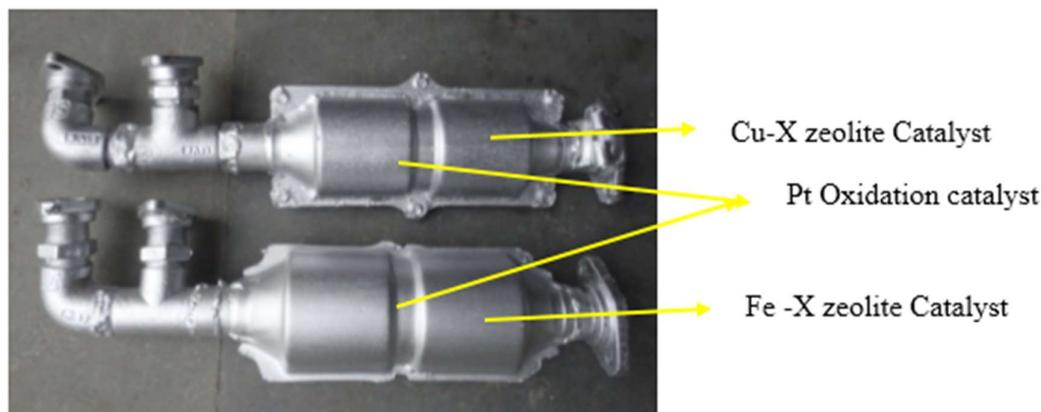


Fig. 5: Depiction of the in-house built deNO_x catalytic converter.

Table 2: Specification of Petrol Engine.

Type	Vertical In-line Engine with MPFI
Number of cylinders	2
Displacement	624 cc
Bore	73.5 mm
Stroke	73.5 mm
Compression Ratio	9.5:1
Fuel	Petrol
Cycle	4-Stroke
Max. Engine output	25.74 kW @ 5250 rpm
Max. Torque	48 Nm @ 3000 rpm
Speed	2500 rpm
Orifice Diameter	20 mm
Cooling System	Water
Loading Device	Eddy current dynamometer

gas temperatures were monitored using strategically placed Chromel-Alumel thermocouples at three distinct locations on the converter.

Initially, standard engine performance was established by operating the engine without a catalytic converter across a range of loads (4, 7, 10, 13, and 16 kW) while sustaining a constant speed of 2500 rpm. Emissions of HC, CO, CO₂, O₂, and NO_x were methodically recorded for each load condition. Thereafter, in Fig. 7, a commercially available catalytic converter was affixed to the engine exhaust manifold, ensuring axial entry of the exhaust gases. The engine was then operated under the Equivalent load and speed conditions previously used for the baseline measurements, and emissions of HC, CO, CO₂, O₂ and NO_x were again recorded. This comparative testing procedure was replicated using both the Fe-zeolite and Cu-zeolite converters. Emissions measurements were conducted under the same operating


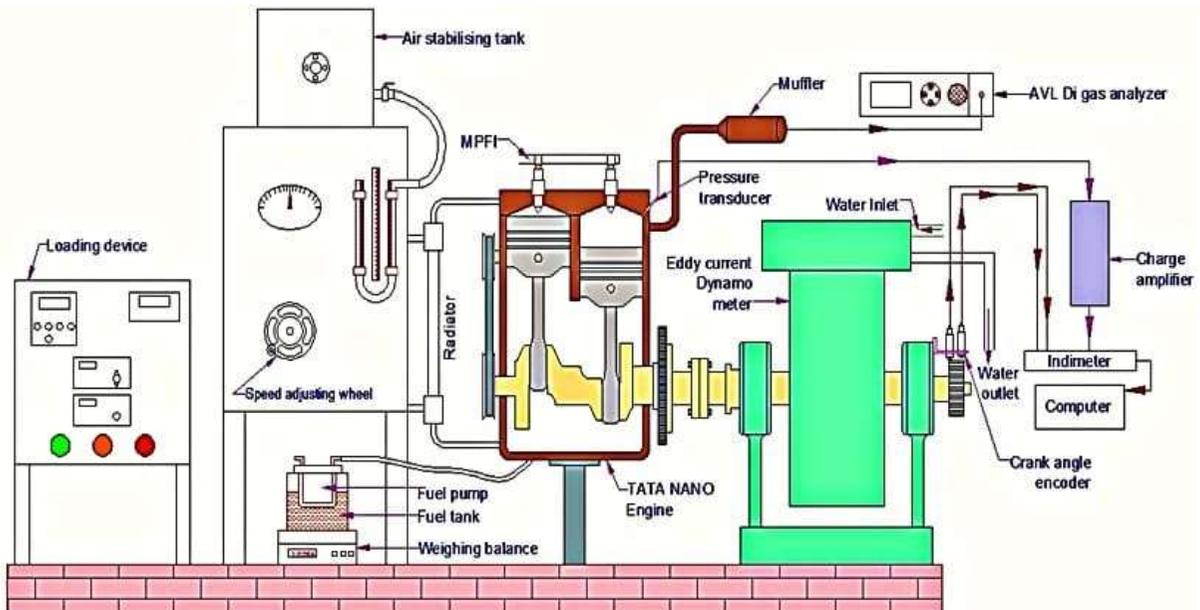


Fig. 6: Experimental setup of petrol engine.



Fig. 7: Photographic view of a catalytic converter fitted in the engine.

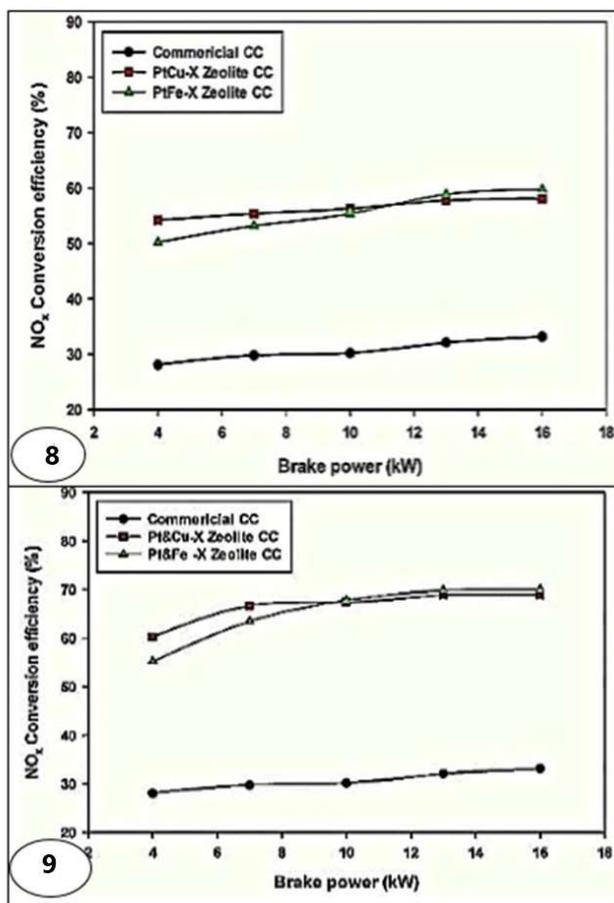

Figs. 8 & 9: Percentage reduction of NO_x Vs. load (dual layer) and Percentage reduction of NO_x Vs. load (deNO_x).

conditions to rigorously evaluate the performance of these in-house fabricated converters against the commercially available unit.

RESULTS AND DISCUSSION

A twin-cylinder, MPFI petrol engine, connected to an eddy current dynamometer, was used for the experiments. The conversion efficiencies were then determined using the following calculations:

- NO_x Conversion Efficiency = $(\text{Inlet NO}_x - \text{Outlet NO}_x) / \text{Inlet NO}_x * 100$
- HC Conversion Efficiency = $(\text{Inlet HC} - \text{Outlet HC}) / \text{Inlet HC} * 100$
- CO Conversion Efficiency = $(\text{Inlet CO} - \text{Outlet CO}) / \text{Inlet CO} * 100$

Nitrogen Oxides Emission with Load

Figs. 8 and 9 demonstrate the NO_x reconfiguration efficiency at various engine loads. The data clearly demonstrate that all

in-house developed catalytic converters achieve significantly higher NO_x conversion than the commercial converter. This effectiveness arises because commercial catalytic converters are designed for stoichiometric air–fuel ratios. However, the engine used is a lean-burn Multi Point Fuel Injection (MPFI) engine, resulting in oxygen-rich exhaust, which negatively affects the efficiency of conventional converters. To resolve this, a more effective catalytic system utilizing zeolite X was developed to diminish NO_x emissions. Zeolite active sites exhibit a high affinity for NO, facilitating its separation into nitrogen (N) and oxygen (O). As shown in the results, enhanced conversion efficiency is observed with the introduced system. While in Figs. 8 and 9, it is seen that the double-layer monolith catalytic converters (Pt-Cu-X zeolite and Pt-Fe-X zeolite) exhibit lower performance compared to the combined monolith catalytic converters (Pt & Cu-X zeolite and Pt & Fe-X zeolite). Notably, the Pt-Fe-X zeolite converter achieves approximately 50% NO_x conversion at a 4 kW load, gradually increasing to about 59% at 16 kW. In contrast, the Pt & Fe-X zeolite converter reduces NO_x by roughly 55% at 4 kW and 70% at 16 kW.


The dual-layer catalytic converter's performance is limited because it requires simultaneous reactions of CO, HC, and NO_x, restricting NO_x reduction to the channel corners. Distinctly, the combined Pt and Fe-x zeolite monolith catalyst offers more active sites, enhancing NO_x conversion. This occurs as exhaust gas flows through the platinum monolith, facilitating NO decomposition into adsorbed nitrogen and oxygen. The nitrogen atoms then combine to form N₂, and the oxygen reacts with CO to produce CO₂. However, at a 4 kW load, the Pt and Cu-X zeolite catalyst showed superior performance compared to the Pt-Fe-X zeolite catalyst.

This performance difference can be attributed to the fact that three reactions (the reduction of CO, HC, and NO_x to CO₂, H₂O, and N₂) occur simultaneously within the dual-layer catalytic converter, limiting the active NO_x reduction sites to the corners of the monolith channels. The combined monolith catalytic converter (Pt & Fe-X) provides more active sites for NO_x conversion, leading to improved performance. As exhaust gas passes through the platinum (Pt) monolith and subsequently contacts the deNO_x monolith, the following reactions occur: (i) NO is adsorbed onto the active metal sites and dissociates into adsorbed nitrogen (N


(ads)) and oxygen (O (ads)), (ii) two N (ads) atoms combine to form N₂, and (iii) the dissociated O (ads) reacts with the remaining CO in the exhaust gas to produce CO₂. At a 4 kW load, the Pt & Cu-X catalytic converter demonstrated better performance than the Pt and Fe-X catalytic converter.

Effects of Exhaust Gas Temperature on Nitrogen Oxide Emission Levels

The relationship between exhaust gas temperature and NO_x conversion efficiency is compared in Figs. 10 and 11. The dual-layer catalytic converter demonstrates a progressive, albeit gradual, increase in efficiency, achieving a 50% NO_x conversion rate at approximately 300°C. Conversely, the combined monolith catalytic converter (deNO_x) exhibits a remarkably rapid surge in conversion efficiency, attaining a 60% conversion rate at approximately 190°C. This enhanced performance continues to improve steadily up to 500°C, beyond which any further significant enhancements are negligible. It is well-established that catalytic converter efficiency is profoundly influenced by temperature. It is expected that the zeolite catalyst will begin to function at approximately 180°C. Below 150°C,

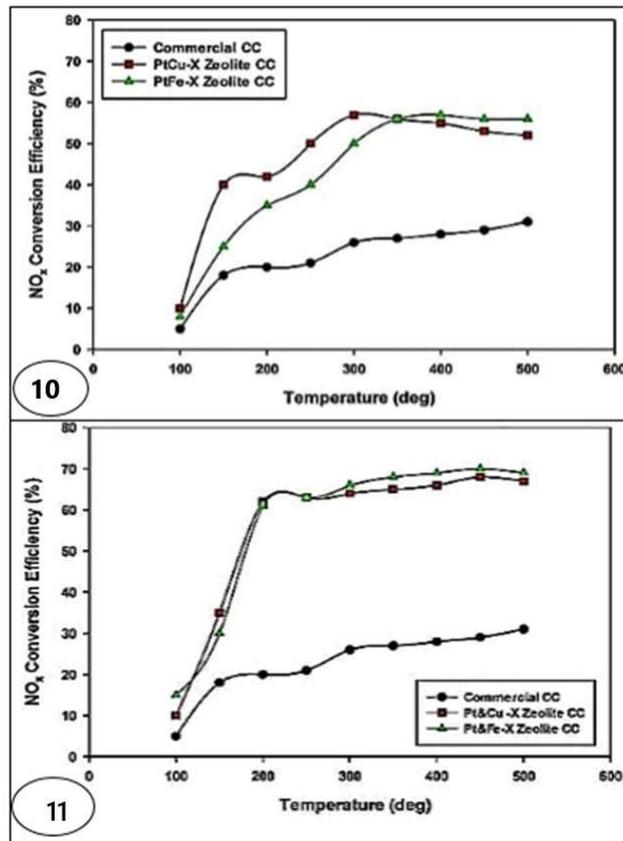

Figs. 10 & 11: Percentage reduction of NO_x Vs. Temperature (dual layer) and percentage reduction of NO_x Vs. temperature (deNO_x).

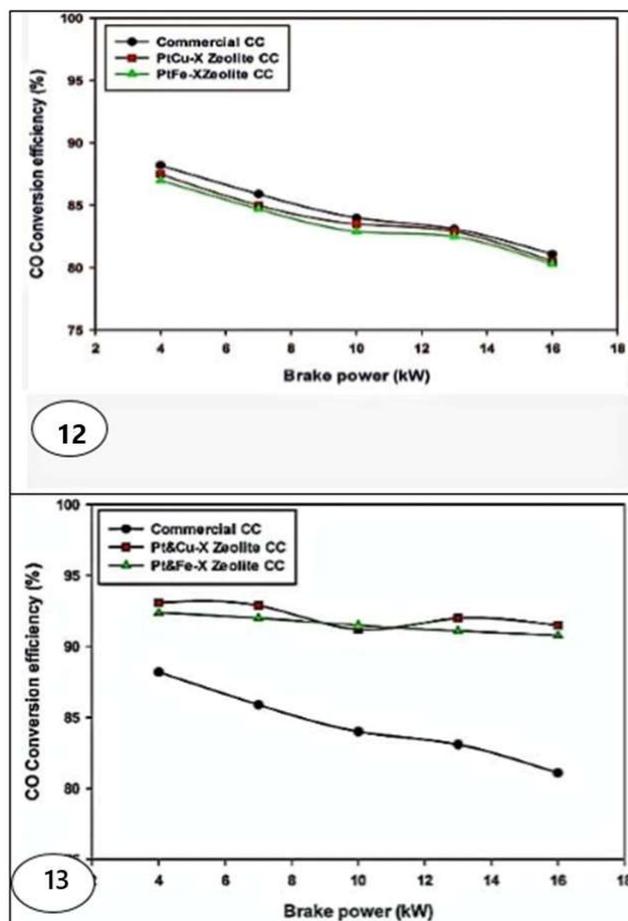

Figs. 12 & 13: Carbon monoxide against brake power (dual layer) and Carbon monoxide against brake power (deNO_x).

its catalytic activity decreases. However, exceeding 180°C triggers a notable activation of the zeolite, resulting in a substantial improvement in NO_x conversion efficiency. This temperature-dependent behavior is conspicuously absent in conventional commercial converters, which often struggle to achieve effective NO_x reduction in oxygen-rich exhaust environments.


CO Conversion Efficiency

Figs. 12 and 13 show the CO conversion efficiencies of both the dual-layer monolith catalytic converter and the deNO_x catalytic converter. Previous studies (Alkemade et al. 2006) have shown that commercial monoliths effectively reduce CO and HC emissions under lean exhaust conditions. Fig. 12 denotes only a slight decrease in CO changeover efficiency compared to the commercial catalytic converter. This is likely because the platinum (Pt) layer in the dual-layer monolith is partially obscured by the zeolite layer, reducing the number of active sites available for CO conversion.


Fig. 13 illustrates that the deNO_x catalyst achieves approximately 93% CO conversion efficiency at a 4 kW load, increasing to nearly 95% at 16 kW. The improved performance is due to residual CO from the Pt-coated monolith reacting with adsorbed oxygen on the deNO_x catalyst, resulting in CO₂ formation. Prior studies have shown that CO oxidation aids NO_x reduction in metal-exchanged zeolite catalysts.

Efficiency of Hydrocarbon Conversion

Figs. 14 and 15 show the percentage reduction in HC emissions as a function of engine brake power. The dual-layer catalytic converter achieves 72% HC conversion at a 4kW load, increasing to 79% at 16Kw. The deNO_x converter system, however, achieves approximately 90% HC conversion at 4 kW, rising to 93% at 16 kW. This higher conversion is attributed to the reaction of unreacted HC emissions exiting the Pt-coated catalyst with adsorbed oxygen, producing CO₂ and H₂O. As demonstrated in earlier work (Liu et al. 2016),

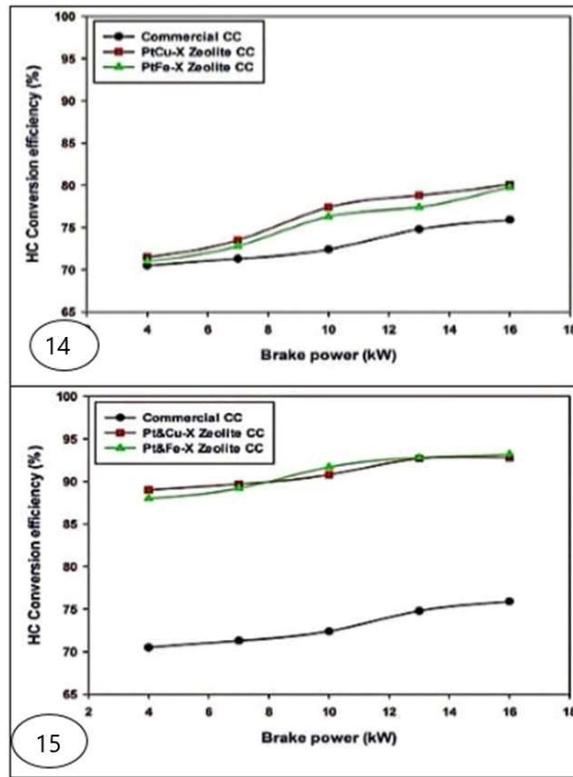

Figs. 14 & 15: Hydrocarbon against brake power (dual layer) and Hydrocarbon against brake power (deNOx).

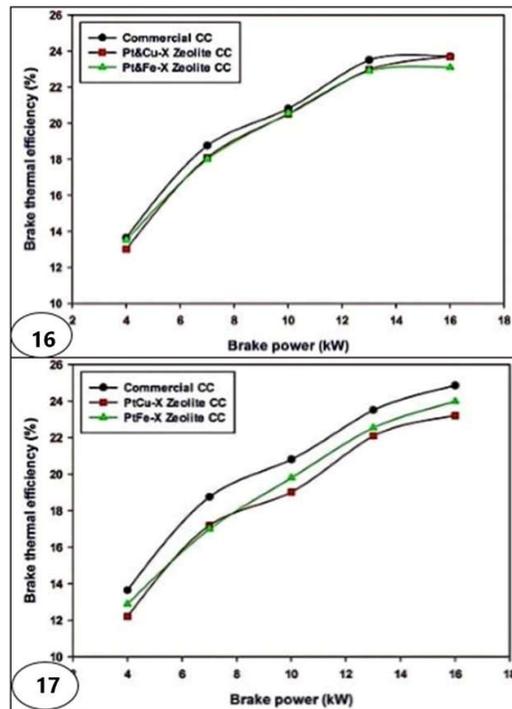

Figs. 16 & 17: Brake thermal efficiency against brake power (dual layer) and deNOx Performance: Brake Thermal Efficiency as a Function of Brake Power.

hydrocarbons act as reducing agents by removing adsorbed oxygen generated during NO_x dissociation. This action preserves the reduced states of the active sites (Cu⁺ or Fe⁺), which facilitates further NO_x reduction.

Brake Thermal Efficiency

Figs. 16 and 17 present a comparative analysis of the engine's thermal efficiency in relation to its brake power output. A subtle yet discernible reduction in brake thermal efficiency is observed when employing the dual-layer monolith catalytic converter, as opposed to the commercially available counterpart. This diminution can be attributed to the marginally increased flow resistance encountered by the exhaust gases as they traverse the monolith walls. The introduction of an additional wash coating layer within the monolith channels effectively reduces the overall flow area, thereby impeding gas flow. Conversely, the deNO_x system demonstrates a brake thermal efficiency that closely mirrors that of the commercial catalytic converter. Notably, despite the inclusion of two distinct monoliths, the deNO_x system does not introduce any significant flow resistance within the exhaust gas pathway.

CONCLUSION

This study suggests a potential alternative to conventional three-way catalytic converters for reducing NO_x emissions from gasoline engines. The synthesized rice husk ash-based Na-X zeolite catalysts, modified with copper and iron ions (Cu-X and Fe-X), demonstrated superior NO_x reduction compared to the conventional converter while maintaining comparable performance for other pollutants. The enhanced performance can be attributed to the unique structural properties of the zeolite-based catalysts and the synergistic effect of the copper and iron ions. These findings indicate that the developed Cu-X and Fe-X zeolite catalysts show promise as a cost-effective and environmentally friendly option for reducing NO_x emissions from gasoline engines. Further research and development are needed to optimize their

- The custom-made metal-doped X zeolite converter outperformed the commercially available one. Performance and scale up production for commercial applications.
- Cu- zeolite X was more effective at reducing NO_x in cooler conditions, whereas Fe- zeolite X excelled at higher temperatures.
- Both carbon monoxide and hydrocarbon emissions were substantially lowered across all engine loads and during speed variation tests.
- The catalyst bed did not create excessive back pressure.

- The catalytic converter showed no noticeable loss of activity after 50 h of testing.

ACKNOWLEDGEMENT

The researchers expressed their gratitude to Annamalai University, Department of Mechanical Engineering, Research Lab, so that it can run well and get results that can benefit the academic world.

REFERENCES

- Alkemada, U.G. and Schumann, B., 2006. Engines and exhaust after treatment systems for future automotive applications. *Solid State Ionics*, 177(26-32), pp.2291-2296.
- Dalai, A.K., Rao, M.S. and Gokhale, K.V.G.K., 2010. Synthesis of NaX zeolite using silica from rice husk ash. *Industrial & Engineering Chemistry Product Research and Development*, 24(3), pp.465-468. [DOI]
- Das, S.K., Adediran, A., Kaze, C.R., Mustakim, S.M. and Leklou, N., 2022. Production, characteristics, and utilization of rice husk ash in alkali activated materials: An overview of fresh and hardened state properties. *Construction and Building Materials*, 345, pp.128341-128360. [DOI]
- Edanol, Y., Usman, K., Buenviaje, S., Mantua, M. and Payawan, L., 2018. Utilizing silica from rice hull for the hydrothermal synthesis of zeolite Y. *KIMIKA*, 29(1), pp.17-21.
- Hassan, A. and Jaaron, A., 2021. Total quality management for enhancing organizational performance: The mediating role of green manufacturing practices. *Journal of Cleaner Production*, 308, pp.127366-127380. [DOI]
- Lee, J.H., Kwon, J.H., Lee, J.W., Lee, H.S., Chang, J.H. and Sang, B.I., 2017. Preparation of high-purity silica originated from rice husks by chemically removing metallic impurities. *Journal of Industrial and Engineering Chemistry*, 50, pp.79-85. [DOI]
- Liu, X., Li, Z., Chen, H., Yang, L., Tian, Y. and Wang, Z., 2016. Rice husk ash as a renewable source for synthesis of sodium metasilicate crystal and its characterization. *Research on Chemical Intermediates*, 42(5), pp.3887-3903. [DOI]
- Ma, Y., Yan, C., Alshameri, A., Qiu, X. and Zhou, C., 2014. Synthesis and characterization of 13X zeolite from low-grade natural kaolin. *Advanced Powder Technology*, 25(2), pp.495-499. [DOI]
- Pandiangan, K.D., Arief, S., Jamarun, N. and Simanjuntak, W., 2017. Synthesis of zeolite-X from rice husk silica and aluminum metal as a catalyst for transesterification of palm oil. *Journal of Materials and Environmental Science*, 8(5), pp.1797-1802.
- Saceda, J.J.F., Leon, R.L.D., Rintramee, K., Prayoonpokarach, S. and Wittayakun, J., 2011. Properties of silica from rice husk and rice husk ash and their utilization for zeolite Y synthesis. *Química Nova*, 34(8), pp.1394-1397. [DOI]
- Saleh, N.J., Al-Zaidi, B.Y.S. and Sabbar, Z.M., 2018. A comparative study of Y zeolite catalysts derived from natural and commercial silica: Synthesis, characterization, and catalytic performance. *Arabian Journal for Science and Engineering*, 43(10), pp.5819-5836. [DOI]
- Santasnachok, C., Kurniawan, W., Salim, C. and Hinode, H., 2014. The utility of rice husk ash from biomass power plant: Synthesis of Na-A and Na-X zeolites using the two-step hydrothermal method. *Journal of Advanced Agricultural Technologies*, 1(2), pp.75-81.
- Setthaya, N., Pindi, C., Chindaprasirt, P. and Pimraksa, K., 2013. Synthesis of faujasite and analcime using rice husk ash and metakaolin. *Advanced Materials Research*, 770, pp.209-212. [DOI]
- Yusof, A.M., Nizam, N.A. and Rashid, N.A.A., 2010. Hydrothermal conversion of rice husk ash to faujasite-types and NaA-type of zeolites. *Journal of Porous Materials*, 17(1), pp.39-47.